

Firing Chart: Cycle B L

°C


Ramp	Rate °C/h	Time Minutes	Temp. °C	Hold Minutes
I	200	160	538	25
II	330	25	650	40
III	SKIP	0	482	50
IV	60	150	370	-
V	100	200	40	-

°F

Ramp	Rate °F/h	Time Minutes	Temp. °F	Hold Minutes
I	360	160	1000	25
II	595	25	1200	40
III	SKIP	0	900	50
IV	110	150	700	-
V	180	200	105	-

Please Read: This firing recommendation has been calculated for use with Bullseye Glass of average viscosity with an even thickness of 4 - 6 mm. The chart shown below is also based on the assumption that you are using a top fired kiln, e.g. Paragon GL22, GL24, BVD Flat bed kilns etc.

If you are using a side firing kiln you must allow more time in the first ramp.

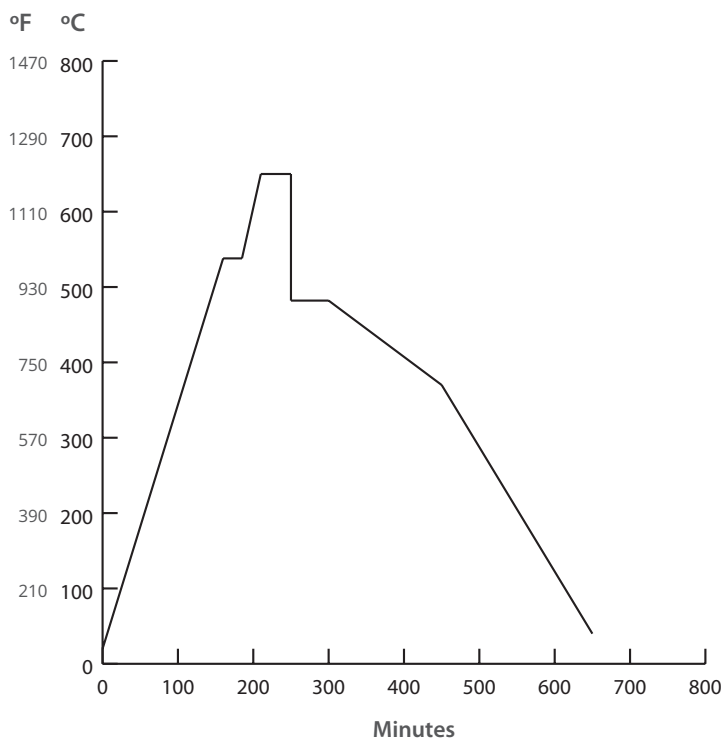

The following moulds are recommended to be fired with this Cycle:

958.042 958.292
 958.043 958.324
 958.051 958.325
 958.052 958.344
 958.121 958.356
 958.126 958.398
 958.133 958.406
 958.138 958.410
 958.139