

# Firing Chart: Cycle D1 L

°C

Ramp	Rate °C/h	Time Minutes	Temp. °C	Hold Minutes
I	200	160	538	25
II	330	25	660	60*
III	SKIP	0	482	50
IV	60	150	370	-
V	100	200	40	-


°F

Ramp	Rate °F/h	Time Minutes	Temp. °F	Hold Minutes
I	360	160	1000	25
II	595	25	1220	60*
III	SKIP	0	900	50
IV	110	150	700	-
V	180	200	105	-

**Please Read:** This firing recommendation has been calculated for use with Bullseye Glass of average viscosity with an even thickness of 4 - 6 mm. The chart shown below is also based on the assumption that you are using a top fired kiln, e.g. Paragon GL22, GL24, BVD Flat bed kilns etc.

**If you are using a side firing kiln you must allow more time in the first ramp.**

**\*visual check necessary. As soon as the slumping process is completed, advance to the next ramp.**

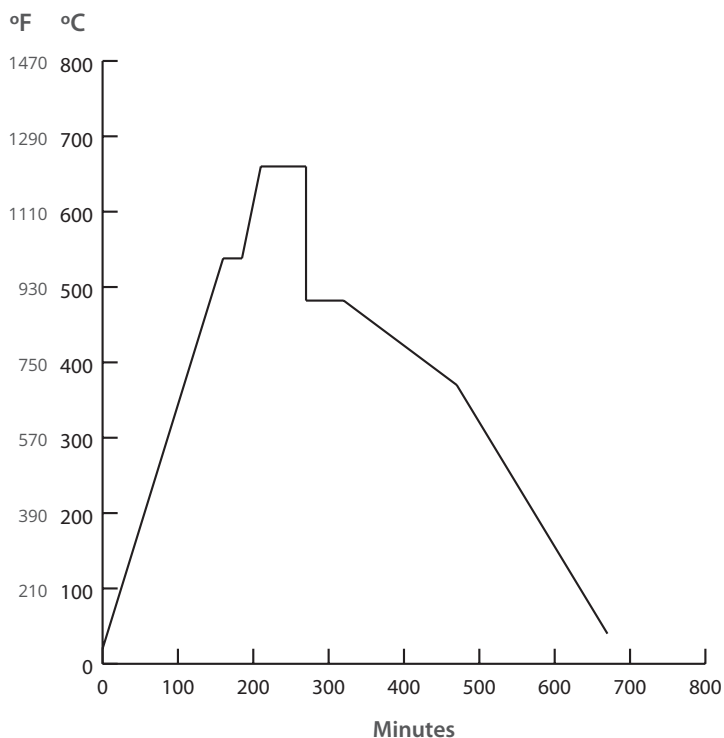

**The following moulds are recommended to be fired with this Cycle:**

958.256  
958.323