

Firing Chart: Cycle S8 L

°C

Ramp	Rate °C/h	Time Minutes	Temp. °C	Hold Minutes
I	200	160	520	25
II	330	40 or 0	735 or 680	45 - 60 * or 120
III	SKIP	0	516	50
IV	60	150	370	-
V	100	200	40	-


°F

Ramp	Rate °F/h	Time Minutes	Temp. °F	Hold Minutes
I	360	160	970	25
II	595	40 or 0		45 - 60 * or 120
III	SKIP	0	960	50
IV	110	150	700	-
V	180	200	105	-

Please Read: This firing recommendation has been calculated for use with Bullseye Glass of average viscosity with an even thickness of 4 - 6 mm. The chart shown below is also based on the assumption that you are using a top fired kiln, e.g. Paragon GL22, GL24, BVD Flat bed kilns etc.

If you are using a side firing kiln you must allow more time in the first ramp.

*visual check necessary. As soon as the slumping process is completed, advance to the next ramp.

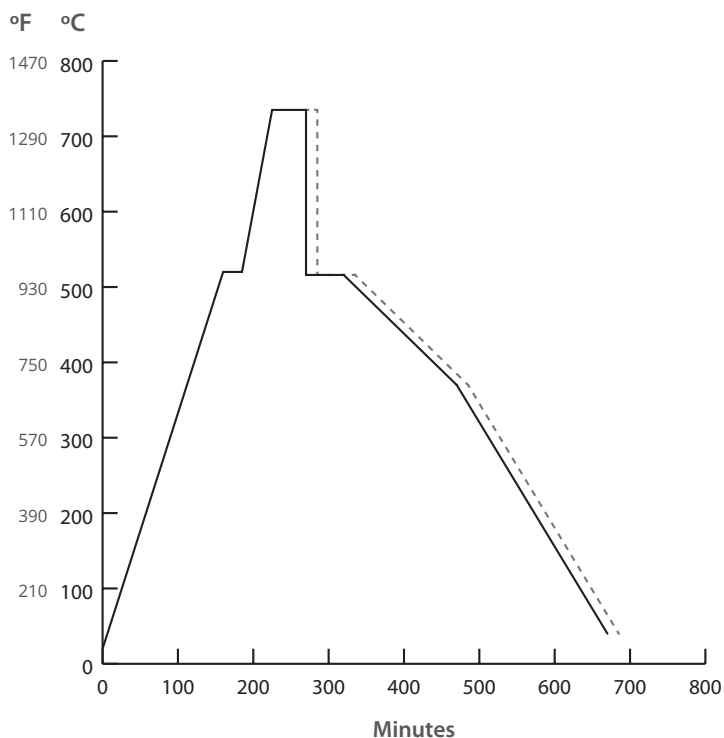

The following moulds are recommended to be fired with this Cycle:

958.290